



FINISHES & CORROSION

PLAIN (PL)

Plain finish designation means that the product retains the oiled surface applied to the raw steel during the forming process. The fittings have the original oiled surface of the bar-stock material.

PVC COATING (PVC)

PVC coating helps reduce noise and protect the pipe or tubing from the metal surface of the hanger. Corrosion resistance protection is minimal. PVC coating is not compatible with CPVC pipe.

COPPER COLOR EPOXY FINISH (CCEF)

Designed for use with copper tubing. This coating provides a better level of corrosion resistance than the traditional copper plated finish. It also acts as a protective barrier, avoiding contact between dissimilar metals. The copper color epoxy powder is applied by an elec-trostatic method, and the coated parts are baked at 180 degrees for 20 minutes.

POWDER COATING (PTD)

PHD Manufacturing, Inc. offers a polyester powder coating that utilizes powder material conforming to ASTM D3451. It is applied by means of an electrostatic spray at ambient temperature.

CHANNEL GREEN: POLYESTER

POWDER PROPERTIES

Test Method	Powder Properties	Tolerances
ASTM D3451 (18.30)	Specific Gravity	1.33 ± 0.03
ASTM D3451 (18.30)	Theoretical Coverage	144.58 ± 4.0 FT ² /Lb./Mil.
ASTM D3451 (13)	Volatile Content	Max. 2.5%
ASTM D3451 (13)	Storage Temperature Max	80°F

COATING PROPERTIES

All tests performed on substrate 0.032 CRS Pretreatment
Bonderite 1000

Test Method	Coating Properties	Tolerances/Specifications
ASTM D523	Gloss 20°/60°	70-80
ASTM D2454	Over Bake Resistance Time	100%
ASTM D3363	Pencil Hardness	H - 2H
ASTM D2794 (Modified)	Direct Impact (Gardner)	80 in. Lbs.
ASTM D2794 (Modified)	Reverse Impact (Gardner)	80 in. Lbs.
ASTM D3359	Adhesion (Cross Hatch)	Pass No Adhesion Loss
ASTM D522	Flexibility (Mandrel)	1/8 Bend No Fracture
ASTM B117	Salt Spray	1000 Hrs.
ASTM D2247	Humidity	500 Hrs.

APPLICATION

Test Method	Application	Cure Schedule
Electrostatic Spray	Ambient Temperature	15' @ 375°F (190°C) Recommended Minimum Film Thickness 1.5

EPOXY E-COAT

PHD Manufacturing's epoxy E-Coat offers state of the art corrosion resistance with out the use of heavy metals such as lead, chrome, and zinc. It is applied to our products by a controlled cathodic electro-deposition process. This process is accomplished by transporting the product through several cleaning, phosphatizing, rinsing, and application stages prior to being baked for 20 minutes at 375°F (190°C).

EPOXY PROPERTIES

Property	Test Method	Performance
Color	---	Various
Film Thickness	---	0.5 - 1.5 Mils
Gloss - 60 Degree	ASTM D523	65 - 85
Pencil Hardness	ASTM D3363	2H Minimum
Direct Impact	ASTM D2794	120 in-lb Minimum
Reverse Impact	ASTM D2794	100 in-lb Minimum
Cross-Hatch Adhesion	ASTM D3359	4B - 5B
Humidity	ASTM D1735	1000 Hours Minimum
Water Immersion	ASTM D870	250 Hours Minimum
Gravelometer	GM 9508P	6 Minimum
Throwpower	GM 9535P	12 - 15 Inches

All tests performed on Cold Rolled Steel Lab Panels, Zinc Phosphate Pretreatment, 0.6 Mil Average Film Thickness, Cure 20 Minutes @ 375°F

Property	Substrate / Pretreatment	Salt Spray* 500 hrs.	Salt Spray* 1000 hrs.	20 Cycle** Scab
Corrosion Resistance	CRS/Zinc Phos/Non-Chrome	0 in. (0 mm)	0 - 0.039 in. (0 - 1 mm)	0.039 - 0.079 in. (1 - 2 mm)

(Average Total Scribe Creep), * Salt Spray - ASTM B117

** Cycle Scab - GM9511P, Cold Rolled Steel Lab Panels

Cure 20 Minutes @ 375°F (190°C)

ZINC COATING

PHD offers 3 basic forms of zinc coating on its products:

- 1) **Electro-Galvanized** (Electro-Plated Zinc)
- 2) **Pre-Galvanized**
- 3) **Hot Dipped Galvanized**

For best results, a zinc rich paint should be applied to field cuts. The zinc rich paint will provide immediate protection for these areas and eliminate the short time period for galvanic action to “heal” the damaged coating.

Note: The corrosion resistance of zinc is based on its thickness, the environment, and the coating process used. The acceptability of galvanized coatings at temperatures above 450°F is at the discretion of the end user.

Zinc offers two types of protection:

- **Barrier:** The zinc coating protects the steel substrate from direct contact with the environment
- **Sacrificial:** The zinc coating will protect scratches, cut edges, etc... through an anodic sacrificial process.

ELECTRO-GALVANIZED “EG” (ASTM B633 SC1 & SC3)

This type of coating is recommended for use indoors in relatively dry areas. The steel is submersed in a bath of zinc salts, through the process of electrolysis, a coating of pure zinc adheres to the steel with a molecular bond. A maximum of 0.5 mils of zinc per side can be applied using this method.

SC1 (Mild) is the standard finish thickness which has a zinc coating of 0.2 mils per side. SC3 (Severe) has a zinc coating of 0.5 mils per side.

PRE-GALVANIZED “PG” (ASTM A653 COATING G90)

This type of coating is suitable for extended exposure in dry or mildly corrosive atmospheres but not generally recommended for use outdoors in industrial environments. Also known as “mill galvanized” or “hot-dipped mill galvanized” pre-galvanized zinc coatings are produced by rolling the steel coils or sheets through molten zinc, at the steel mill, the material is then cut or slit to size. Zinc near the uncoated edges or weld areas becomes a sacrificial anode which protects the bare areas.

The pre-galvanized material conforms to ASTM A653 with a G90 zinc coating. The zinc thickness per side is nominally 0.75 mils thick or 0.45 oz /sq ft.


HOT-DIP GALVANIZED “HDG” (ASTM 123)

Recommended for prolonged outdoor exposure and will usually protect steel in most atmospheric environments. After fabrication the part is im-mersed in a bath of molten zinc. A metallurgical bond is formed resulting in a zinc coating that coats all surfaces including edges. Please note that some items cannot be hot-dipped galvanized due to design, tolerances, or threaded components. Check with the PHD factory or your local representative when questionable. Threaded components on hot dipped galvanized products will be electro-plated.

The hot-dip galvanized coating is typically 2.6 mils or 1.5 oz /sq ft per side.

As shown in the graph, when the zinc coating is double, the service life is double under most conditions.

Life of Protection vs. Thickness of Zinc
And Type of Atmosphere

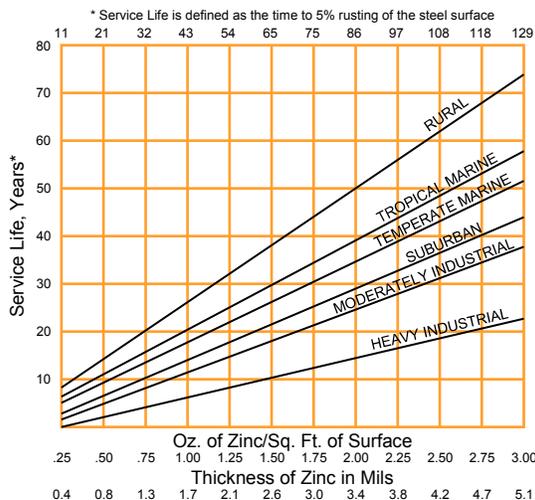

Comparison of Zinc Finishing	
Finish	Zinc Thickness (mils)
Hot-Dip Galvanized	2.6
Pre-Galvanized	0.75
Electro-Galvanized (SC1)	0.2
Electro-Galvanized (SC3)	0.5